arXiv:cond-mat/0507582v1  [cond-mat.str-el]  25 Jul 2005

# Uniaxial pressure dependencies of the phase boundary of $TlCuCl_3$

N. Johannsen [a], A. Oosawa [b], H. Tanaka [c], A. Vasiliev [d], and T. Lorenz [a,*]
[a] *II. Physikalisches Institut, Universität zu Köln,Zülpicher Str. 77, 50937 Köln, Germany*
[b] *Advanced Science Research Center, Japan Atomic Energy Research Institute, Tokai, Ibaraki 319-1195, Japan*
[c] *Department of Physics, Tokyo Institute of Technology, Oh-okayama, Meguro-ku, Tokyo 152-8551, Japan*
[d] *Department of Low Temperature Physics, Moscow State University, Moscow 119992, Russia*

---

## Abstract

We present a thermal expansion and magnetostriction study of $TlCuCl_3$, which shows a magnetic-field induced transition from a spin gap phase to a Néel ordered phase. Using Ehrenfest relations we derive huge and strongly anisotropic uniaxial pressure dependencies of the respective phase boundary, e.g. the transition field changes by about ±185 %/GPa depending on the direction of uniaxial pressure.

*Key words:* magnetoelastic coupling, low-dimensional magnets, Bose-Einstein condensation
*PACS:* 75.30.Kz,75.80.+q,65.40.De

---

The magnetic subsystem of $TlCuCl_3$ may be viewed as a set of three-dimensionally coupled spin dimers with a singlet ground state. Due to the rather strong interdimer couplings the first excited triplet state has a pronounced dispersion and as a consequence the minimum spin gap $\Delta \simeq 8\,K$ is significantly smaller than the intradimer coupling $J \simeq 64\,K$.[1] Thus a magnetic field of about 6 T is sufficient to close $\Delta$. Above 6 T a field-induced Néel order with transverse staggered magnetization is observed,[2] which has been described by a Bose-Einstein condensation of magnons.[1] The ground state of $TlCuCl_3$ is very sensitive to pressure, hydrostatic pressure of order 0.5 GPa is sufficient to induce the Néel order already in zero magnetic field.[3] In order to obtain more information about this drastic influence of pressure we performed high-resolution measurements of the thermal expansion $\alpha_i = \partial \ln L_i/\partial T$ and the magnetostriction $\epsilon_i = (L_i(H) - L_i(0))/L_i(0)$ and derive the uniaxial pressure dependencies of the transition temperatures and fields.

Fig. 1 shows $\alpha_i$ perpendicular to the (010) and $(10\overline{2})$ cleavage planes of $TlCuCl_3$ measured for different magnetic fields. In zero field $\alpha_{010}$ ($\alpha_{10\overline{2}}$) shows a broad maximum (minimum) around 18 K. This anomalous temperature dependence can be traced back to a Schottky anomaly of $\alpha_i$ due to the thermal population of the triplet state with $\Delta$ depending on uniaxial pres-

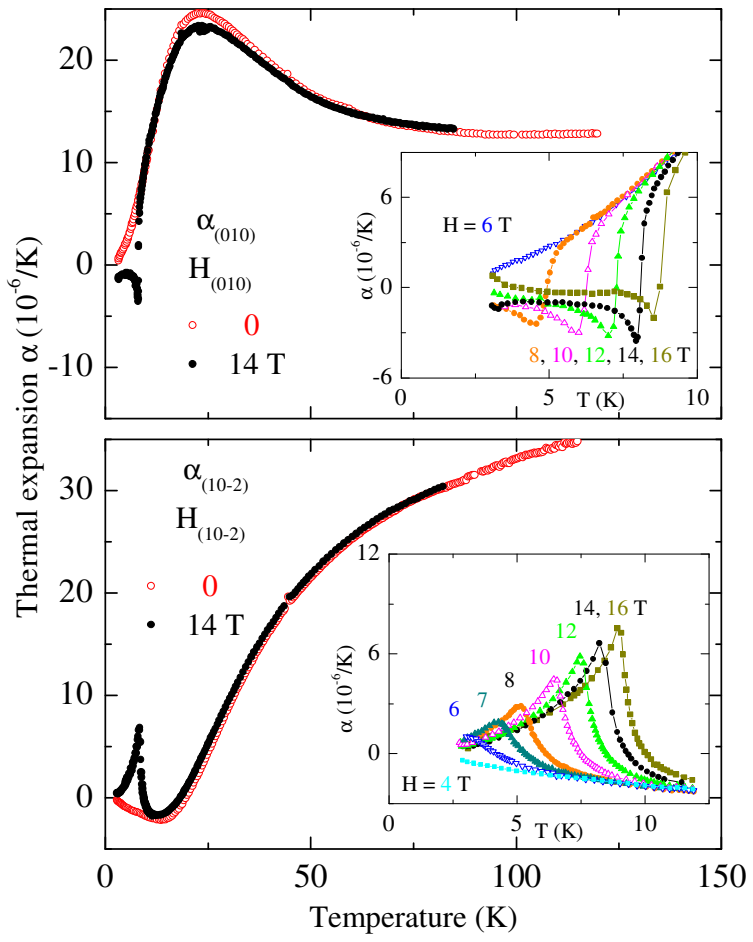

Fig. 1. Thermal expansion $\alpha_i$ perpendicular to the (010) and the $(10\overline{2})$ cleavage planes of $TlCuCl_3$ for different magnetic fields $(H||\alpha_i)$.

---

[*] Corresponding author:
*Email address:* `lorenz@ph2.uni-koeln.de` (T. Lorenz).

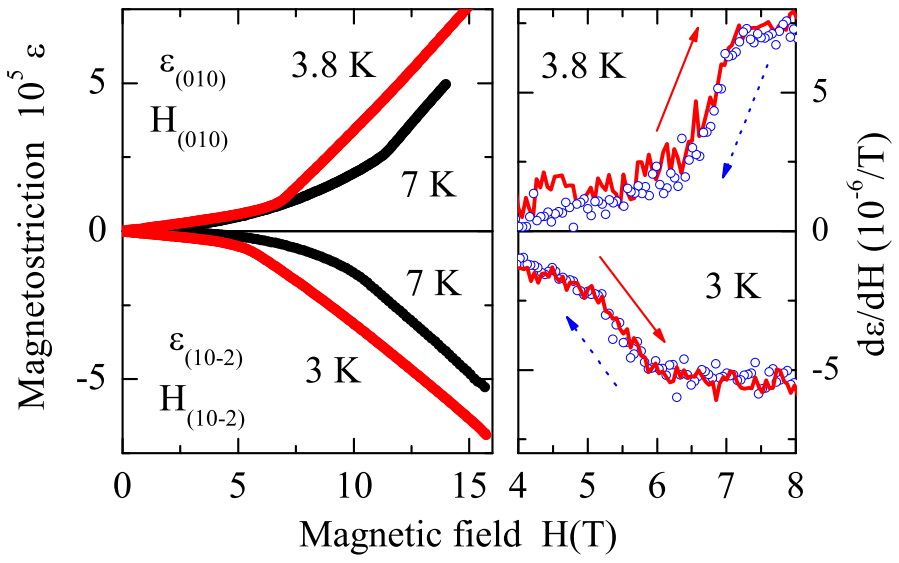

Fig. 2. Left: Longitudinal magnetostriction $\epsilon_i$ ($H||\epsilon_i$) perpendicular to the (010) and the ($10\overline{2}$) cleavage planes of TlCuCl$_3$ at different temperatures. Right: Field derivatives $\partial\epsilon_i/\partial H$ from the measurements with increasing (—) and decreasing (○) field.

sure $p_i$. The opposite signs signal that $\partial\Delta/\partial p_{010} > 0$ and $\partial\Delta/\partial p_{10\overline{2}} < 0$. A magnetic field hardly changes $\alpha_i$ above about 10 K, but for lower $T$ well-defined anomalies develop for $H > 6$ T, which arise from the above-mentioned Néel order. The anomalies are of opposite signs for both directions. Fig. 2 displays representative magnetostriction measurements. The field-induced Néel order causes a kink in $\epsilon_i$ leading to a jump-like change of $\partial\epsilon_i/\partial H$ (again of opposite signs). The $\partial\epsilon_i/\partial H$ curves obtained with increasing and decreasing field hardly differ from each other and we do not detect a hysteresis of $H_c$. Thus, our data agree with the expected behavior of a second-order phase transition and disagree with an ultrasound study showing a large hysteresis of order 0.5 T for $H_c$.[4]

The phase diagram obtained from our data (Fig. 3) well agrees with previous results.[5] A power-law fit of the form $(g/2)[H_c(T)-H_c(0)] \propto T^\Phi$ yields $\Phi = 2.6$ and $H_c(0) = 5.6$ T (with the $g$ factor for the respective field direction [5]). The value of $\Phi$ agrees with that obtained by Quantum Monte Carlo (QMC) simulations. [6] The QMC studies also reveal that $\Phi$ sensitively depends on the temperature range of the fit, what may explain why the experimental $\Phi$ obtained at finite $T$ is much larger than the expected critical exponent $\Phi = 1.5$ at $T \to 0$ K for a Bose-Einstein condensation.

Using Ehrenfest relations our data together with specific heat ($C_p$) and magnetization ($M$) data allow to calculate the uniaxial pressure dependencies

$$\frac{\partial T_c}{\partial p_i} = V_m\, T_c\, \frac{\Delta\alpha_i}{\Delta C_p} \quad \text{and} \quad \frac{\partial H_c}{\partial p_i} = V_m \frac{\Delta\frac{\partial\epsilon_i}{\partial H}}{\Delta\frac{\partial M}{\partial H}}\,. \tag{1}$$

Here, $V_m$ is the molar volume, $\Delta\alpha_i$ is the anomaly size of $\alpha_i$ (see Fig. 1) and $\Delta C_p$ that of $C_p$ [5], $\Delta\frac{\partial\epsilon_i}{\partial H}$ is the slope change of $\epsilon_i$ at $H_c$ (see Fig. 2) and $\Delta\frac{\partial M}{\partial H}$ that of $M$ [7]. In Fig. 3 we show some expected $T_c$ and $H_c$ values for a hypothetical uniaxial pressure $p_i = 0.1$ GPa with $p_i$ perpendicular to the (010) (▲) and ($10\overline{2}$) (▼) planes. The Néel phase is strongly destabilized by $p_{010}$ and stabilized by $p_{10\overline{2}}$. The dashed lines represent power-law fits of the pressure-shifted phase boundaries. Their extrapolations to $T = 0$ K yield for the ambient-pressure spin gap $\Delta = g\mu_B H/k_B \simeq 7.5$ K and huge values for its uniaxial pressure dependencies: $\partial \ln\Delta/\partial p_{10\overline{2}} \simeq -180$ %/GPa and $\partial \ln\Delta/\partial p_{010} \simeq +190$ %/GPa. The respective signs of $\partial \ln\Delta/\partial p_i$ agree to those of the Schottky anomalies of $\alpha_i$. Hydrostatic pressure also strongly stabilizes the Néel phase,[3] but due to the opposite signs the $\partial \ln\Delta/\partial p_i$ nearly cancel each other. Thus we conclude that uniaxial pressure parallel to the [201] direction, which is perpendicular to both of our measurement directions, will also strongly decrease $\Delta$. Analyzing the relation between the uniaxial pressure dependencies of $\Delta$ and of the magnetic susceptibility around 30 K yields that both arise from a pressure-dependent intradimer coupling.[8]

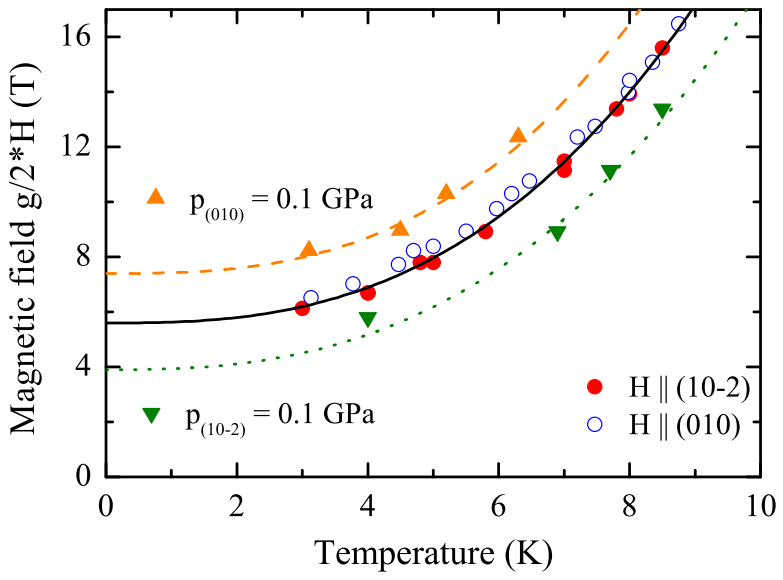

Fig. 3. Phase diagram of TlCuCl$_3$ from the magnetostriction and thermal expansion measurements perpendicular to the (010) (○) and ($10\overline{2}$) (●) planes. The triangles display the calculated shift of $T_c$ and $H_c$ values for a uniaxial pressure of 0.1 GPa perpendicular to (010) (▲) and ($10\overline{2}$) (▼). The lines are power-law fits of the phase boundaries.

In summary, the field- and temperature-dependent changes of different lattice constants yield huge and strongly anisotropic uniaxial pressure dependencies of the spin gap leading to drastic changes of the phase diagram of TlCuCl$_3$.

This work was supported by the DFG via SFB 608.

## References

[1] T. Nikuni et al, Phys. Rev. Lett. **84** (2000) 5868; M. Matsumoto et al, Phys. Rev. Lett. **89** (2002) 077203; Ch. Rüegg et al, Nature **423** (2003) 62.

[2] H. Tanaka et al, J. Phys. Soc. Japan **70** (2001) 939; A.Oosawa et al, Phys. Rev. B **66** (2002) 104405.

[3] A. Oosawa et al, J. Phys. Soc. Japan **72**, (2003) 1026; H. Tanaka et al, Physica B **329** (2003) 697.

[4] E. Ya. Sherman et al, Phys. Rev. Lett. **91** (2003) 057201.

[5] A. Oosawa et al, Phys. Rev. B **63**, 134416 (2001).

[6] S. Wessel et al, Phys. Rev. Lett. **87** (2001) 206407; O. Nohadani et al, Phys. Rev. B **69** (2004) 220402(R).

[7] W. Shiramura et al, J. Phys. Soc. Japan **66** (1997) 1900.

[8] N. Johannsen et al, Phys. Rev. Lett. **95** (2005) 017205.